



# V S 7 1 2 曲げクリープ試験

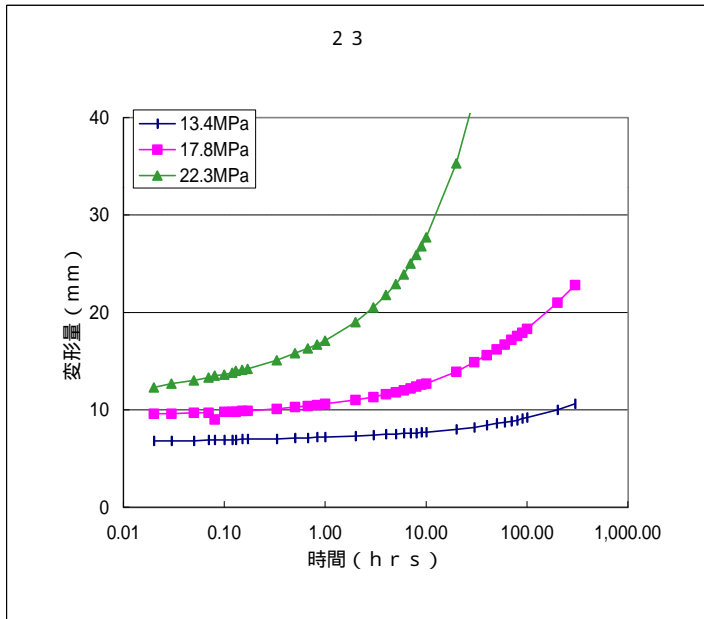


2 3

	13.4MPa	17.8MPa	22.3MPa
0.02	6.8	9.6	12.3
0.05	6.8	9.7	13.0
0.10	6.9	9.8	13.6
0.15	7.0	9.9	14.1
0.50	7.1	10.3	15.8
1	7.2	10.6	17.1
2	7.3	11.0	19.0
4	7.5	11.6	21.8
8	7.6	12.4	25.9
20	8.0	13.9	35.3
40	8.4	15.6	49.1
100	9.2	18.3	
200	10.0	21.0	
300	10.6	22.8	

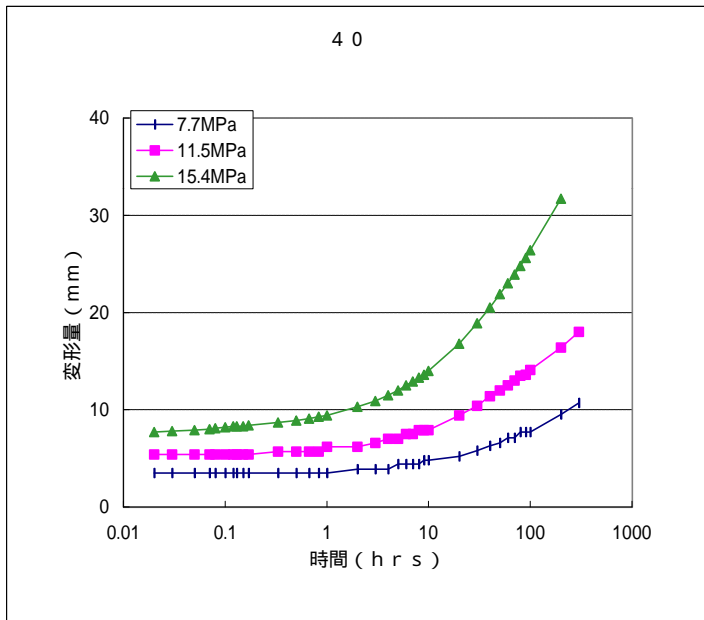

4 0

	7.7MPa	11.5MPa	15.4MPa
0.02	3.5	5.4	7.7
0.05	3.5	5.4	7.9
0.10	3.5	5.4	8.2
0.15	3.5	5.4	8.3
0.50	3.5	5.7	8.9
1	3.5	6.2	9.4
2	3.9	6.2	10.3
4	3.9	7.0	11.5
8	4.4	7.9	13.3
20	5.2	9.4	16.8
40	6.3	11.4	20.5
100	7.7	14.1	26.4
200	9.5	16.4	31.7
300	10.7	18	

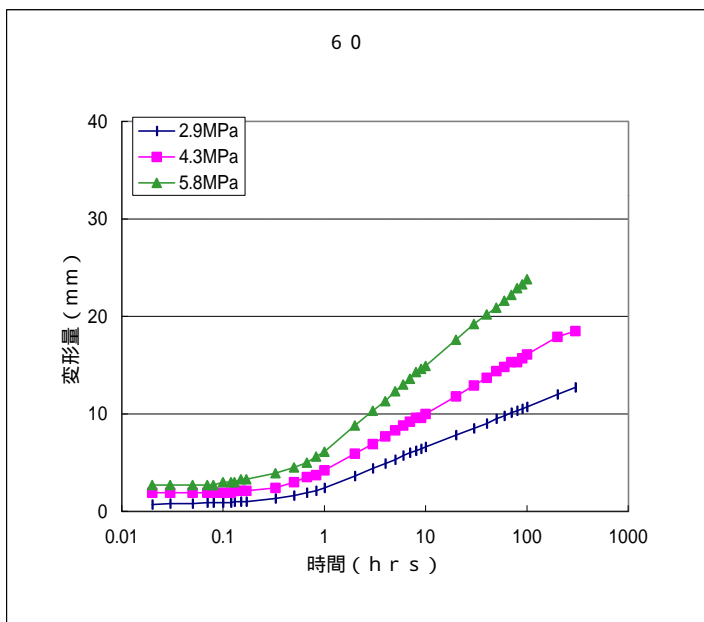

6 0

	2.9MPa	4.3MPa	5.8MPa
0.02	0.7	1.9	2.7
0.05	0.8	1.9	2.7
0.10	0.9	1.9	3.0
0.15	1.0	2.1	3.3
0.50	1.6	3.0	4.5
1	2.4	4.2	6.1
2	3.6	5.9	8.8
4	4.9	7.7	11.3
8	6.2	9.6	14.3
20	7.8	11.8	17.6
40	9.0	13.7	20.2
100	10.7	16.1	23.8
200	12.0	17.9	
300	12.7	18.5	